

SUMITUBE™

SUMITUBE™ B2

[Flexible flame-retarded heat-shrinkable tubing]
SAE/UL/CSA recognized

Catalog No. 826 RoHS directive 10 substances

Waterproofing Flame-retarded UL recognized CSA recognized



Basic Properties

- **Material** : Irradiated cross-linked flexible flame-retarded polyolefin
- **Shrink temperature** : min. 90°C
- **Shrink ratio** : Radial change: min. 50%
: Longitudinal change: 0 ±5%
- **Continuous operating temperature** : -55 to 135°C

Features

- SAE/UL/CSA recognized
- Flame-retarded (PBDE/PBB-free)
- Flexible ■ Bright colors

Specifications/Approvals

SAE-AS23053/5 Class 1, 3
UL224 File No. E48762 Catalog No. SUMITUBE™ B2 or 826
Rating temperature: 125°C Rating voltage: 600V Flammability: VW-1
CSA C22.2 No. 198.1 File No. LR33298
Rating temperature: 125°C Rating voltage: 600V Flammability: VW-1

Applications

- Insulation, protection and reinforcement for termination and joints of electric wire
- Color identification and bundling for electric wires
- Insulation and protection of resistors and capacitors

Properties [SAE-AS23053/5 Class 1]


Properties	Items	Requirements	Typical values*1
Mechanical	Tensile strength (before aging)	min. 10.4MPa	13.4MPa
	Elongation (before aging)	min. 200%	410%
	Elongation (after aging)	175°C x 7 days, min. 100%	410%
	Low temperature flexibility	-55°C x 4 hours, no crack	Pass
	Heat shock	250°C x 4 hours, no crack	Pass
Electrical	Dielectric strength	min. 19.7kV/mm	37.1kV/mm
	Volume resistivity	min. 1.0 x 10 ¹⁵ Ω·cm	3.1 x 10 ¹⁵ Ω·cm
Chemical	Water absorption	23°C x 24 hours, max. 0.50%	0.28%
	Corrosion against bare copper	175°C x 16 hours, no corrosion	Pass
	Color stability	175°C x 24 hours, no change	Pass
	Fluid resistance	After im mersion in the fluids specified in SAE-AS23053 at 23°C for 24 hours,	
	Tensile strength	min. 6.9MPa	13.1MPa
	Dielectric strength	min. 15.8kV/mm	30.5kV/mm
	Flammability(UL224)	Flame-retarded, pass VW-1	Pass

*1: For reference use only

Sizes

Trade size (inch)	As supplied (mm)		After recovered (mm)		Unit length (min.) (m)	
	Inside diameter	Wall thickness (nom.)	Inside diameter (max.)	Wall thickness	Cut	Spool
3/64	1.60 ±0.30	0.20	0.60	0.41 ±0.07	1.22	305
1/16	2.00 ±0.30	0.20	0.80	0.43 ±0.07	1.22	305
3/32	2.70 ±0.30	0.25	1.20	0.51 ±0.07	1.22	152.5
1/8	3.50 ±0.30	0.25	1.60	0.51 ±0.07	1.22	152.5
3/16	5.20 ±0.30	0.30	2.40	0.51 ±0.07	1.22	61
1/4	6.8 ±0.4	0.30	3.20	0.64 ±0.07	1.22	61
3/8	10.0 ±0.4	0.30	4.75	0.64 ±0.07	1.22	61
1/2	13.2 ±0.5	0.30	6.4	0.64 ±0.07	1.22	61
3/4	20.0 ±0.6	0.40	9.5	0.76 ±0.07	1.22	61
1	26.6 ±0.8	0.45	12.7	0.89 ±0.12	1.22	61
1-1/2	39.3 ±1.0	0.45	19.1	1.02 ±0.15	1.22	61
2	52.7 ±1.5	0.50	25.4	1.14 ±0.17	1.22	61
3	77.7 ±1.5	0.55	38.1	1.27 ±0.20	1.22	61
4	106.0 ±3.0	0.60	50.8	1.40 ±0.22	1.22	30.5

Shrink Properties

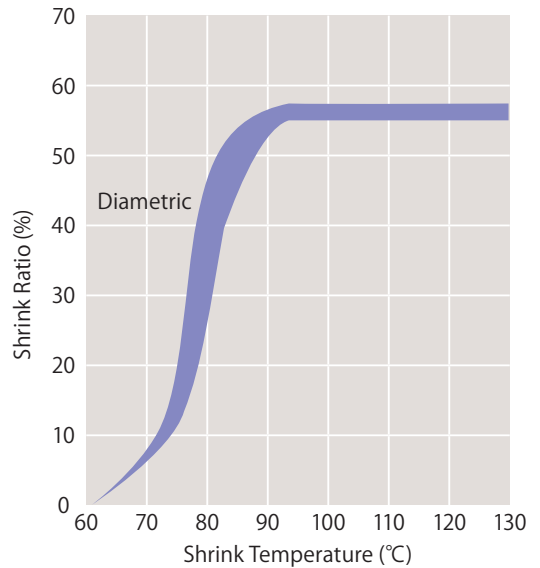

Colors

- Black, Brown, Red, Orange, Yellow, Green, Blue, Purple, Gray, White
- Note: Yellow/Green striped color is available only for limited sizes
- Yellow/Green has no SAE recognized

IRRX™TUBE
IRRX™TAPE

- A
- B
- F2
- F2 (UL)
- V2
- RP3
- B8
- ER2
- NHR
- FE2
- IRRXTAPE VZL

IRRX™SLEEVE

- SCM2
- IRRXSLEEVE SBI 300/350
- SNHM

Composite articles

- SUMISEAL
- SUMITUBE SA3 CAP

Processing equipment

SUMISHRINKER / HEATING GUN



SCATTERGOOD & JOHNSON LTD

ELECTRICAL ENGINEERING & FLUID CONTROL DISTRIBUTORS

Est.1899

At Scattergood & Johnson Ltd, we pride ourselves on being a technical distributor to specialist industries.

Working with a range of quality product suppliers across a number of specialist markets, we are not your average 'box shifter' - we are your technical and supply chain partner.

We fully support every product we sell - for free! Our internal team and external sales engineers can answer any product or application question, no matter the complexity.

Backing up this technical ability is a range of 50,000+ products available from stock for nationwide next day delivery (same day if required!), or you can collect what you need from any of our trade counters around the UK.

Select your specialist interest below to learn more about how we can help.



Online, In Branch and On the Road - Scattergood & Johnson Ltd, there when you need us.

www.scatts.co.uk